

Technical Information

5350 Series Capacitor Dielectric System

The 5350 capacitor dielectric system consists of four standard blendable members. Pastes with lower dielectric constant than 50 are available as special items, e.g., 5350-25 is K25 and 5350-10 is K10. This barium titanate based system is suitable for the integration of capacitors in thick film microcircuits, as well as for the manufacture of discrete components. The thermal expansion of these materials is well matched to that of 96% alumina, resulting in dense films. Capacitors may be buried

under or within layers of multilayer systems. Key features of the system include:

- Blendability Across the Full Range
- Firing in Standard 850°C Profile.
- Compatibility with 100% Ag, Ag:Pd, and Gold Electrodes.
- Tight TCC: X7R
- Laser Trimmable with Ag:Pd Electrode.
- Passivation with High or Low Temperature Overglaze.

TYPICAL FIRED FILM CHARACTERISTICS⁽¹⁾

	5350	5351	5352	5355
Dielectric Constant ⁽²⁾	50 ± 15%	100 ± 15%	250 ± 15%	500 ± 15%
Dissipation Factor @ 1KHz, 25°C	≤ 1.0 %	≤ 1.2 %	≤ 1.5 %	≤ 2.0 %
Insulation Resistance (IR) Ohms @ 50VDC	≥ 10 ¹²	≥ 10 ¹²	≥ 10 ¹²	≥ 10 ¹¹
Fired Thickness Microns	34-45	34-45	34-45	34-45
Dielectric Strength VDC @ recommended thickness	≥ 600	≥ 600	≥ 600	≥ 600
Temperature Characteristic ⁽³⁾	X7R	X7R	X7R	X7R

(1) Typical properties are based on testing of several batches under various processing conditions. They are not intended as specification limits.

(2) The electrical results are based on 0.100" x 0.100" capacitors fabricated with 5350 series dielectrics and 6111 or 6120 silver pastes. Three layers of dielectric were utilized to achieve the recommended fired film thickness.

(3) The X7R designation means a maximum capacitance (dielectric constant) shift of $\pm 15\%$ from -55°C to $+125^{\circ}\text{C}$.

COMPOSITION PROPERTIES

Viscosity: 170 ± 30 Kcps, when measured with Brookfield HBT viscometer, Spindle #14, utility cup, 10 rpm, 25°C

Specific Gravity: 3.0 - 3.5 g/cm³

Recommended Thinner: KOARTAN A-1039


RECOMMENDED PROCESSING PROCEDURE

Printing: For best results, three separate print/dry/fire operations with 325 mesh stainless steel screen using 10-15 μm emulsion and 45 degree angle is recommended. Each printing operation should consist of two wet passes. Other mesh counts, 200-250, and emulsion thicknesses, 5-25 μm , may be used for special applications. A class 10,000 or better clean room should be utilized if only two layers of dielectric are printed. Depending on the print area, squeegee speeds of up to 10 inches/sec may be utilized.

Coverage is approximately 70 cm²/g per layer, when utilizing 325 mesh screen and a wet print thickness of about 35 μm .

Drying: Wet prints should be allowed to level for 5-10 minutes prior to drying. Dry for 10-15 minutes in a convection oven or belt dryer at 125°C - 150°C .

Firing: Firing in air using a belt furnace and a 36-60 minute profile, with 10 minutes at a peak temperature of 850°C , is recommended. Air flow rates must be optimized to ensure that the products of binder burn-off discharge properly and create a fully oxidizing atmosphere in the muffle.

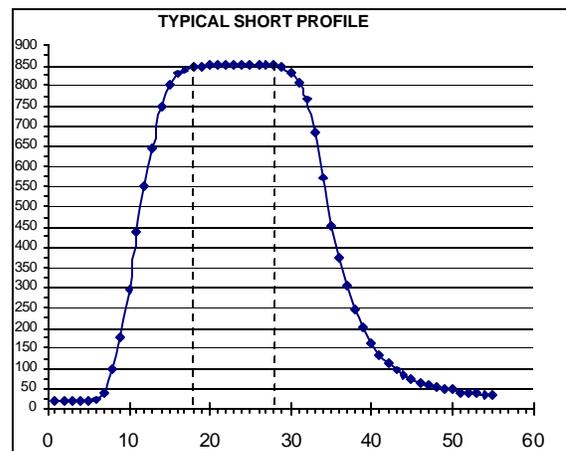

Temperature ($^{\circ}\text{C}$) vs. Time (minutes)

Passivation: Two layers of a hermetic overglaze are recommended. The overglaze must overlap the capacitor by at least .010" all around. Please consult Koartan's technical staff for recommendation for your particular application.

Storage and Shelf Life: Store in tightly capped containers at room temperature. Shelf life is 6 months for unopened jars. Thorough mixing of the paste before each use is recommended. Under ordinary conditions of storage and use the product should not require thinning. However, solvent loss during extended printing runs may be corrected by incorporating up to 0.5% of Koartan A-1039 thinner.

The information presented herein is based on data believed to be dependable and is accurate and reliable to the best of our knowledge and belief, but not guaranteed to be so. Koartan Company assumes no liability arising from the use of this product or the information provided herein. It is the responsibility of the user to verify the information and to establish the suitability of the product(s) for any particular application. Nothing herein is to be construed as recommending any practice or any product in violation of any patent or in violation of any law or regulation.